

Steel grade

Material No. / Werkstoff-Nr.	PREMIUM 1.2367
Description	X38CrMoV5-3
AISI/SAE	1.2367
Search for alternatives in the ABRAMS STEEL GUIDE [®]	www.steel-guide.eu/alternatives/1.2367

Specifications



€co-Präz* [€co]
L: 500 mm



Precision round steel
with machining allowance [PRS/BA]
peeled / rough-turned
L: 500 mm
L: 1.000 mm

Chemical composition AISI/SAE 1.2367 (reference value %)

C	Si	Mn	P	S	Cr	Mo	V
0,35 - 0,4	0,3 - 0,5	0,3 - 0,5	0 - 0,03	0 - 0,02	4,8 - 5,2	2,7 - 3,2	0,4 - 0,6

Physical properties

Hardness (delivery condition)	max. 229 HB, annealed						
Tensile strength R _m (as received condition)	approx. 770 N/mm ²						
Working hardness	max. 54 HRC						
Thermal expansion coefficient 10 ⁻⁶ m/(m • K)	20 - 100°C	20 - 200°C	20 - 300°C	20 - 400°C	20 - 500°C	20 - 600°C	20 - 700°C
	11,9	12,5	12,6	12,8	13,1	13,3	13,5
Thermal conductivity W/(m • K)	20°C	350°C	700°C				
	Annealed	30,8	33,5	35,1			
	Tempered	29,8	33,9	35,3			

Technical properties

Hot work steel with excellent toughness, excellent heat resistance and excellent tempering resistance. Good hardenability with high warp-resistance. Can be cooled with water.

Applications

Dies, die inserts, extrusion presses, hot extrusion tools, die casting tools, slides, press mandrels, intermediate sleeves, die holders, profiling dies, profile mandrels, block receivers, hot shear knives, light metal processing, plastic moulds.

Heat treatment

	Temperature	Cooling	Hardness						
Soft annealing	730 - 780°C	Furnace	max. 229 HB						
	Temperature	Cooling							
Stress relief annealing	600 - 650°C	Furnace							
	Temperature	Quenching in	Hardness after quenching						
Hardening	1020 - 1050°C	Air, oil, hot basin (500 - 550°C)	57 HRC						
Tempering	100°C	200°C	300°C	400°C	500°C	550°C	600°C	650°C	700°C
	57 HRC	55 HRC	53 HRC	52 HRC	55 HRC	55 HRC	52 HRC	45 HRC	36 HRC

ABRAMS INDUSTRIES[®]
abrams-industries.eu

ABRAMS PREMIUM STEEL[®]
premium-steel.eu

ABRAMS PREMIUM ALUMINIUM[®]
premium-aluminium.eu

ABRAMS[®] PREMIUM TOOLS
premium-gewindebohrer.eu

ABRAMS STEEL GUIDE[®]
steel-guide.eu

Divisions of
ABRAMS Industries GmbH & Co. KG
Hannoversche Str. 38 / 46
49084 Osnabrück
Germany

County court Osnabrück / Germany, HRA 6865
GP: ABRAMS Industries Verwaltungs GmbH
Country court Osnabrück / Germany, HRB 20019
CEO: Dipl.-Wi.-Ing. Dr. Jürgen Abrams
COO: Ms. Nur H. Nezir, LL.B.


T: +49 541 / 357 39-0
sales@abrams-industries.eu
www.abrams-industries.eu/shop
VAT-No.: DE221940667

Bank details:
Bank: Sparkasse Osnabrück / Germany
SWIFT / BIC: NOLADE22
IBAN: DE63 2655 0105 1522 9268 96




Thermal expansion coefficient diagram

Werkstoff: X38CrMoV5-3, 1.2367

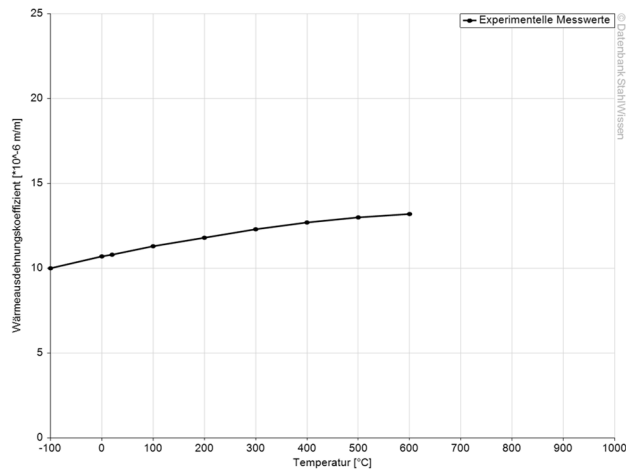


Thermal conductivity diagram

Werkstoff: X38CrMoV5-3, 1.2367

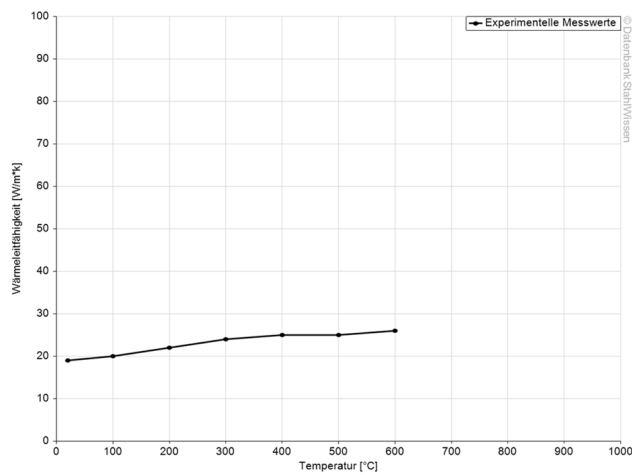


Thermal capacity diagram

Werkstoff: X38CrMoV5-3, 1.2367


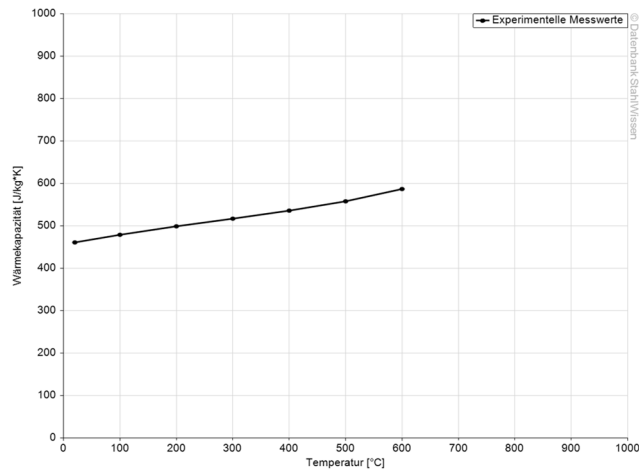


Continuous ZTU-diagram


Werkstoff: X38CrMoV5-3, 1.2367

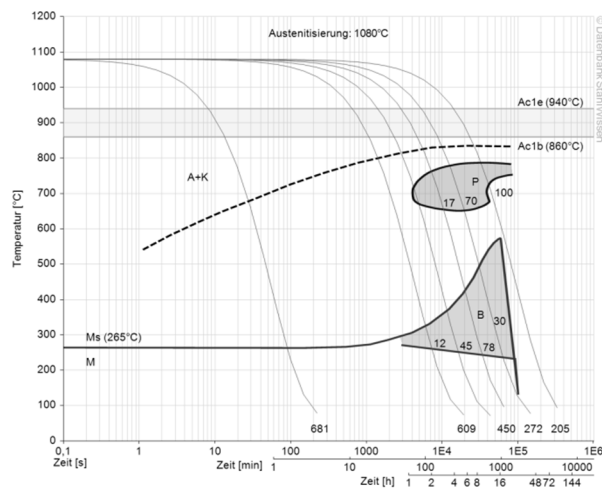

Hardening and tempering diagrams

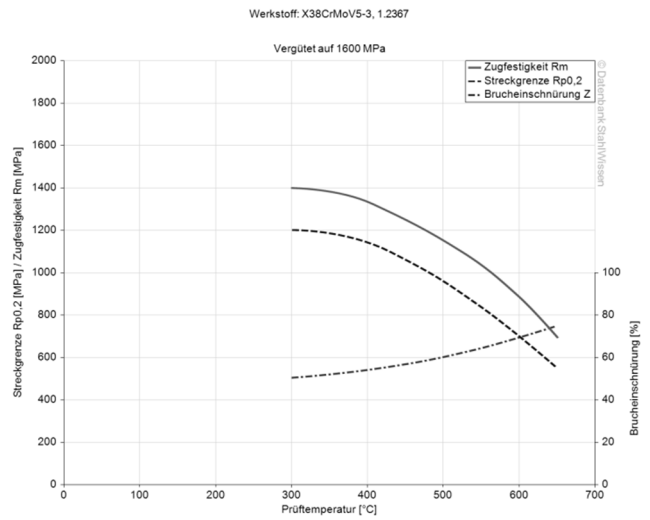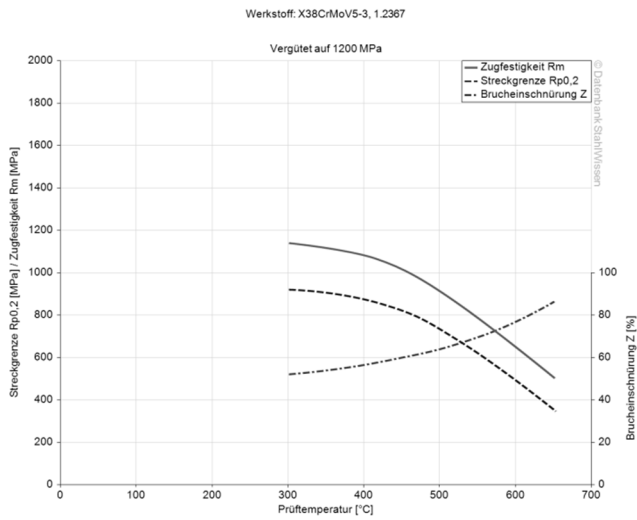

Tempering diagram

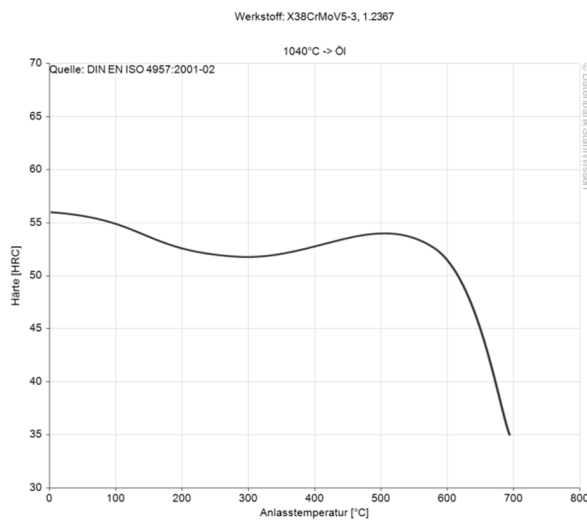

The data shown here is to be used only as an indication of the statistics, thus we accept no liability. Diagrams are taken from Datenbank StahlWissen Dr. Sommer Werkstofftechnik Issued: 2012

